

The oligomerization process was performed in an autoclave from Berghoff (Germany) with the capacity of 200 cm³ made of the chromium-nickel-molybdenic steel. The cover of the autoclave was equipped with: two needle valves, thermocouple, manometer and the safety plate. A weighed amount of the catalyst, previously ground and roasted was put into the dry autoclave, and then 50 cm³ of dry acetonitrile was added. After covering the autoclave some proper amount of HFPO was put under the solvent

while the mixture was stirred intensively. The reaction temperature from -10 to +40°C was maintained by immersing the autoclave in a thermostated water-ethylene glycol mixture. The pressure inside the autoclave was kept constant by means of a second valve connected to a cryostat (-50°C). The products of the HFPO oligomerization were analyzed as methyl esters on the gas chromatograph Chrom 5. The chromatographic conditions: 7m column with the 3mm inner diameter, filled up with 15% Reoplex 100 deposited on the chromosorb WAW 60/80 mesh, program temperature: isothermally at 50°C for 4 minutes and then ramped from 50 to 200°C at 20°C/min rate, detector FID, carrier gas nitrogen 25 cm³/min, the volume of the sample 0.3μl.

RESULTS

Firstly, the dependence of the oligomers HFPO yield in heterogenic oligomerization on the kind of initiators was determined. The other parameters such as the amount of aprotic solvent (50 cm³), the temperature (20°C), the reaction time, pressure and the molar ratio were kept constant. The HFPO oligomerization was performed for 5 hours at 2 atm and a halide : acetonitrile : HFPO the molar ratio of 1 : 10 : 5, respectively. The results received in the oligomerization are presented in Table 1. The results show that by using alkali metal halides, the degree of the HFPO oligomerization decreases in the sentence: F, Cl, Br and I. Oligomerization in the presence of fluoride ion under certain examination conditions leads mainly to trimers and tetramers, in lesser amounts to dimer and pentamer. Iodide ion oligomerizes HFPO mainly to the dimer. The tetramer is created in very little amount. The results correlate well with the sizes of ionic radius of halides and their electronegativity. With the rise in ion radius of the halide its electronegativity decreases, which leads to the decrease of ion nucleophilicity. As a result, a decrease in nucleophilicity leads to a decrease in the average degree of the HFPO oligomerization.

Table 1. The dependence of the degree of the THFP oligomerization on the kind of the catalyst

	Catalyst	Oligomers of THFP, wt%				
		Dimer	Trimer	Tetramer	Pentamer	Heksamer
1	KF	12.3	24.0	38.4	21.8	4.1
2	CsF	13.9	52.8	21.0	11.6	1.2
3	KCl	31.5	46.3	19.0	3.1	—
4	KBr	51.5	40.2	8.4	—	—
5	KI	82.8	12.3	5.6	—	—

The next examined parameter was the dependence of the oligomerization degree on the kind of the solvent. KF was used as the catalyst, the reactions with solvents were performed at 20°C, under 1 atm pressure, for one hour, at the molar ratio of KF : HFPO : solvent = 1 : 50 : 5. The results received are presented in Table 2.

In the next stage, the influence of the temperature on the yield of the HFPO tetramer was examined. The tests were at a temperature range of -10°C to +40°C. Diglyme was used as the solvent and KF as the catalyst. The other conditions were identical as in the previous examinations of the influence of the kind of the catalyst. The received results are presented in Fig. 1.

Table 2. The dependence of the degree of the THFP oligomerization on the kind of the solvent

Solvent	Oligomers					
	n=0	n=1	n=2	n=3	n=4	n=5
Tetrahydrofuran	100	—	—	—	—	—
Acetonitrile	31	53	13	3	—	—
Glyme	24	29	27	14	6	—
Diglyme	17	27	28	20	8	—
Tetraglyme	8	21	30	24	12	5




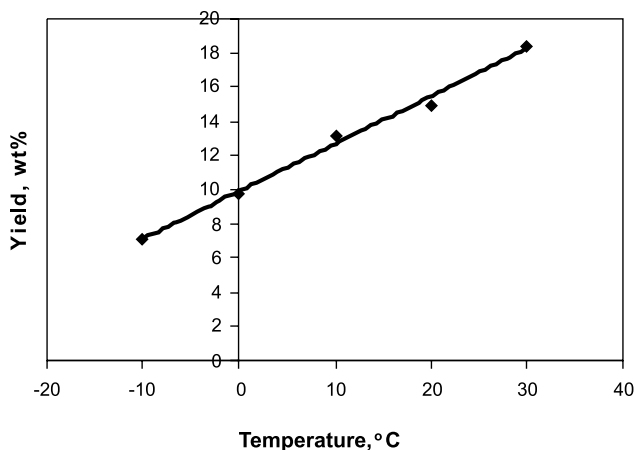


Figure 1. The dependence of the yield of the THFP trimer on the temperature

CONCLUSION

The presented results show that in the presence of alkali metals halides, the best catalysts to obtain trimers and tetramers are potassium and cesium fluoride. The condition for successful oligomerization is anhydrous medium and the maximum granulation of the catalyst. Cesium fluoride has severe disadvantages in this aspect for it is hygroscopic. It is difficult to maintain the conditions, making the work with cesium fluoride demanding. In the catalytic processes with chloride, bromide and iodide ions, there is a possibility to insert these ions to the structure of oligomers, resulting in the reaction illustrated in the following mechanism:



This confirms the phenomenon that oligomers catalyzed by iodine ions take on a bright red color after a long exposure to light.

The next parameter studied was the influence of the aprotic solvent. It was observed that the solubility of halides in the investigated solvents plays an important role. In tetrahydrofuran, alkali metal halides are practically insoluble, thus oligomerization does not proceed in this solvent. Alkali metal halides dissolve poorly in acetonitrile, thus the oligomerization reaction proceeds with

difficulty. The influence of the solubility of halides is most clearly visible in glymes. The more ether oxides in the molecule of glyme the easier and faster the oligomerization proceeds. This is related to the fact that inorganic salts form with ether oxides of the glyme complexes similar to those with crone ethers. The influence of temperature on the course of the oligomerization is minimal. With an increase in temperature there is an increase in the participation of oligomers with $n > 4$.

LITERATURE CITED

- (1) Millauer H., Schwertflegler W., Siegemund G.: Hexafluoropropylene oxide – a key compound in organofluorine chemistry, *Angew. Chem. Int. Ed. Engl.* **1985**, 24, 161.
- (2) Strutz H. at al.: Method for the oligomerization of hexafluoropropene oxide, EP 0378797, **1990**.
- (3) Darling D. T. at al.: Polymerization of hexafluoropropylene oxide, EP 0154297, **1985**.
- (4) Kuhne G at al.: Process for the dimerization of hexafluoropropylene oxide, US Pat. 4303593, **1981**.
- (5) Arbogast F.L at al.: Polymerization of hexafluoropropylene oxide, US Pat. 3412148, **1968**.
- (6) Kruse A. at al.: Verfahren zur herstellung von perfluorierten carbonsaurefluoriden, DE Pat. 3737920, **1989**.
- (7) Kissa E.: Fluorinated surfactants: synthesis, properties, applications, *Surfactant Science series*, Marcel Dekker, New York **1994**.